

Solution Combustion Synthesis and Energy Transfer in LaMgAl₁₁O₁₉:Tb³⁺/Sm³⁺ Tunable Phosphor

S.P. Puppalwar^{1,*}, M.S. Mendhe¹, S.J. Dhoble²

¹Department of Physics, Kamla Nehru Mahavidyalaya, Nagpur 440009, India

²Department of Physics, R.T.M. Nagpur University, Nagpur 440033, India

*Corresponding author: E-mail: suresh.puppalwar@gmail.com; Tel.: (+91) 9881049243

DOI: 10.5185/amlett.2021.021601

Tb³⁺/Sm³⁺ single as well as co-doped LaMgAl₁₁O₁₉ (LMA) phosphors have been synthesized by a low-temperature solution combustion method. The X-ray diffraction pattern, photoluminescence properties and energy transfer (ET) processes between rare earth (RE) ions, were investigated in detail. The mechanism of energy transfer (ET) from Tb³⁺ to Sm³⁺ was seen as the dipole-dipole interaction. Efficient ET from Tb³⁺ to Sm³⁺ ions was observed, leading to color-tunable emissions of LMA:0.02Tb³⁺, x Sm³⁺ (x = 0.005 to 0.02 mol) phosphors. The efficiency of the ET gradually increased with increase in the Sm³⁺ ion concentration, reaching a maximum of 78.28% at Tb³⁺ ion concentration 0.02mol. The critical distance (R_c) among sensitizer and activator by the concentration quenching method was estimated to be 27.96 Å. The LMA: Tb³⁺, Sm³⁺ phosphors exhibited the emission peaks in the blue (⁵D₃→⁷F_J = 5, 4, 3, and 2), green (⁵D₄→⁷F_J = 6, 5, and 4), and orange-red (⁴G_{5/2}→⁶H_J = 5/2, 7/2, and 9/2) regions under the excitation wavelength of 375 nm. As a consequence of fine-tuning of the emission composition of the Tb³⁺ and Sm³⁺ ions, multicolor emitting luminescence properties can be achieved in a single host lattice LMA.

Introduction

The trivalent rare earth (RE) ions (Eu³⁺, Yb³⁺, Ho³⁺, Dy³⁺, Nd³⁺, Tb³⁺, Ce³⁺, Sm³⁺, Er³⁺, Tm³⁺ etc) have been considered as one of the most appropriate candidates for multicolor light emission and even white light emission when they are incorporated into the host matrix. The trivalent RE ions doped phosphors have been gaining importance in recent years due to their fascinating optical properties and the great variety of applications. In optical materials, fluorescence efficiency is the most crucial and significant parameter for their optical applications. In single RE ion doped materials, increase the fluorescence efficiency by increasing the dopant concentration up to appropriate value and then they might be decreased due to concentration quenching effect [1]. To avoid this problem and to yield fruitful results, energy transfer (ET) process between multi-activators is being tried in optical materials. ET process not only improves the fluorescence efficiency but also helpful to adjust the relative intensities of activators. Due to this crucial phenomenon, ET process has become an attractive subject to achieve color-tunable emission or multicolor phosphors during the past decades. Consequently, possible ET process among RE combinations in various materials have been reported earlier, especially Ce³⁺→Tb³⁺, Tb³⁺→Sm³⁺, Tb³⁺→Eu³⁺, Sm³⁺→Eu³⁺, Dy³⁺→Sm³⁺ etc. [2-11]. ET mechanism in potassium-fluoro-phosphate glasses has been investigated for Tb³⁺-Sm³⁺ pair [12]. Li *et al.*, reported the recent development in phosphors with different emitting colors via ET [13]. Recently, our previous work [14,15] reported

an efficient ET from Ce³⁺ to Tb³⁺ in SrYAl₃O₇ and Tb³⁺ to Eu³⁺ in CaLaAlO₄ phosphors.

It is well known that the ⁵D₄→⁷F_J (J = 6, 5, and 4) characteristic emissions of Tb³⁺ ions are mostly in the green region while the ⁴G_{5/2}→⁶H_{J/2} (J = 5, 7, and 9) characteristic emissions of Sm³⁺ ions are mostly in the orange region. At an appropriate concentration of Sm³⁺ ions, the fluorescence efficiency of the Sm³⁺ single doped phosphors might be decreased due to concentration quenching effect. Due to this fluorescence efficiency in orange region of Sm³⁺ doped phosphors is require to increased by secondary RE dopant ion. Tb³⁺ is one of the best secondary RE dopant ions which increased the fluorescence efficiency of Sm³⁺ doped phosphors [16-18].

The LaMgAl₁₁O₁₉ (LMA) lattice belongs to hexagonal of magnetoplumbite-type structure and has attracted much attention due to its excellent chemical and luminescent properties. Synthesis and luminescent properties of orange-red emitting phosphor LaMgAl₁₁O₁₉:Sm³⁺ was reported by Min *et al.* in 2014 [19]; and also reported that the LaMgAl₁₁O₁₉:Sm³⁺, Eu³⁺ was one of the promising red-emitting phosphor for solar cells and near-ultraviolet white light-emitting diodes [20]. To the best of our knowledge, synthesis and photoluminescence (PL) properties of Tb³⁺/Sm³⁺ co-doped LaMgAl₁₁O₁₉ (LMA) phosphors have not been reported. In present work, we choose LMA as a host while Tb³⁺ and Sm³⁺ ions as activators to synthesize a series of LMA: Tb³⁺/Sm³⁺ phosphors through low-temperature solution combustion method. Tb³⁺ has been taken as sensitizing ion and Sm³⁺ as activator ion. We have also reported here the

structural and photoluminescence properties of the prepared phosphors. Furthermore, the ET from the Tb^{3+} to Sm^{3+} ions and dipole-dipole interaction responsible for ET process has been also discussed in details.

Experimental

Materials details

In the present study, low-temperature solution combustion technique by using urea has been employed for the synthesis of Tb^{3+}/Sm^{3+} single as well as co-doped $LaMgAl_{11}O_{19}$ phosphors. The precursors: Lanthanum nitrate [$La(NO_3)_3 \cdot 6H_2O$], Magnesium nitrate [$Mg(NO_3)_2 \cdot 6H_2O$], Aluminum nitrate [$Al(NO_3)_3 \cdot 9H_2O$], Urea [NH_2CONH_2], (all A.R. grade of 99.99 purity – E. Merck) and Terbium nitrate [$Tb(NO_3)_3 \cdot 6H_2O$], Samarium oxide [Sm_2O_3] (both rare earths 99.99% purity - Loba), where metal nitrates are used as oxidizer and urea as a fuel. All these were weighed according to the desired stoichiometric ratio. The heat of combustion is maximum for O/F ratio equal to 1 [21]. Nitrate form of Samarium was obtained by dissolving the Sm_2O_3 into diluted nitric acid and warming these solutions at 50–60 °C for 10–15 min.

Material synthesis

For the synthesis of $LaMgAl_{11}O_{19}:Tb, Sm$, stoichiometric amount of the all reactants lanthanum nitrate, magnesium nitrate, aluminium nitrate, terbium nitrate, prepared nitrate form of samarium and urea were dissolved in 150 ml of H_2O in a 250 ml beaker. The solution was stirred for 30 min and then kept on a magnetic stirrer for 10–20 minutes at 80–100 °C to get uniform mixing and after evaporation of water it get converted into the gel of precursors. This gel in beaker was kept in a muffle furnace at an initiating combustion temperature of 500 ± 20 °C for the burning process. After all the liquid had evaporated, the reagents decomposed and released large amounts of gasses. A large amount of heat released (due to the exothermic nature of this process) resulted in a flame that decomposed the reagents further and released more gasses. The flame lasted for ~60 seconds and the combustion process was completed within 5 minutes. The resulting white foamy and voluminous combustion products were cooled down to room temperature. This foamy mass was ground gently using a pestle and mortar to get a fine powder. $LaMgAl_{11}O_{19}: Tb, Sm$ powder yield to a composition with the general formula $LaMgAl_{11}O_{19}: 0.02Tb, ySm$ ($y = 0.5, 1, 1.5, 2$) for different concentrations of Sm^{3+} . This powder was then used for the further characterizations.

Characterizations

The phase composition and phase structure were measured by X-ray diffraction (XRD) pattern. XRD performed with P-analytical diffractometer with $Cu K\alpha$ radiation ($\lambda = 1.5405 \text{ \AA}$) operating at 40kV, 30mA anode current, was used to identify the major phases of the powders.

These were compared to the JCPDS card for $LaMgAl_{11}O_{19}$. The XRD data were collected in a 2θ range from 10 to 80°, with the continuous scan mode. The morphology and microstructure were characterized with JEOL, JSM-6360LV SEM environmental scanning electron microscope (SEM). The PL excitation and emission spectra were recorded using a RF-5301PC Spectrofluorophotometer fitted with a sensitive photomultiplier tube with a 150W ‘xenon flash lamp’ as an excitation source. The excitation and emission spectra were recorded using a spectral slit width of 1.5 nm with high sensitivity. All the measurements were carried out at room temperature.

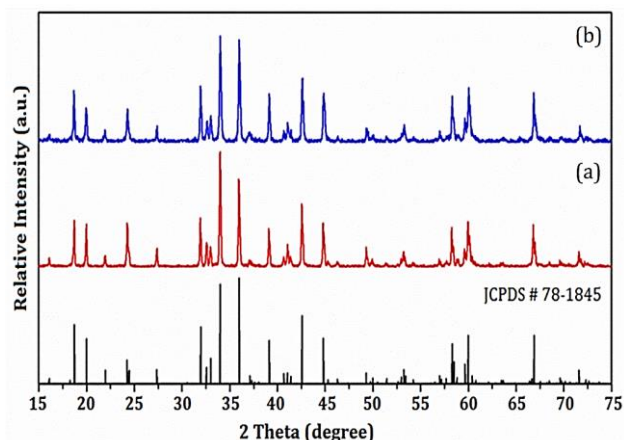


Fig. 1. XRD patterns of (a) pure and (b) Tb^{3+}/Sm^{3+} co-doped LMA phosphors along with standard JCPDS card no. 78-1845.

Results and discussion

Phase analysis and morphology

The phase purity of prepared samples is checked by XRD patterns. The XRD patterns of pure and Tb^{3+}/Sm^{3+} co-doped LMA phosphors along with the standard JCPDS card no. 78-1845 are shown in **Fig. 1**. Both the XRD patterns show well-defined peaks, which reveals the crystallinity and phase formation of the synthesized compounds. The samples exhibit identical diffraction patterns as the standard JCPDS card and confirm that the samples are of the hexagonal structure with space group $P6_3/mmc$ (194). In the XRD pattern, there is no significant influence on the host lattice by the incorporation of a small amount of dopant ions as there are no extra peaks related to the second phase which suggests that the dopant ions completely incorporated to the host. The crystal size is evaluated using the Debye-Scherrer's equation. The average crystal size for prepared sample is found to be in the range of 180-200 nm. **Fig. 2(a-b)** exhibits the SEM micrographs for LMA: Tb^{3+}, Sm^{3+} phosphors at different magnification levels. Reaction in the presence of urea allows the varying size and shape of particles. This irregularity in size and shapes of particles is caused by the non-uniform distribution of temperature and irregular mass flow during combustion process.

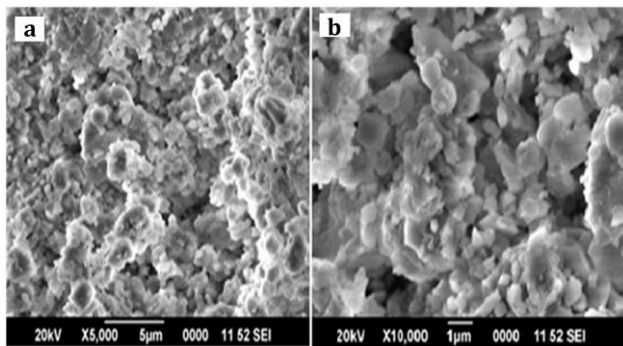


Fig. 2. SEM images of LMA: 2Tb³⁺/1.5Sm³⁺ phosphor.

Optical properties of Tb³⁺ and Sm³⁺ doped LMA

Fig. 3(a) depicts the PL excitation (PLE) spectrum of LMA: Tb³⁺ (2 mol%) phosphor by monitoring emission wavelength of 545 nm. The spectrum consists of a broad band ranging from 240 to 280 nm with the maximum at 260 nm, corresponding to 4f⁸→4f⁷5d¹ transition of Tb³⁺ and a series of spectral bands in the range of 300–400 nm, analogous to the transitions between 4f→4f states of Tb³⁺ [14,22]. The f→f transitions of Tb³⁺ have been properly designated as ⁷F₆→⁵H₇ at 317 nm, ⁷F₆→⁵D₂ at 350 nm and 358 nm, and ⁷F₆→⁵G₆ at 375 nm [23]. PL emission spectra of LMA: Tb³⁺ phosphor with different concentration of Tb³⁺ under the excitation of 260 nm are shown in Fig. 3(b). The PL spectra consist of a series of sharp lines in the 480–600 nm regions. The emission bands at 489, 545, and 571 nm can be attributed to the ⁵D₄→⁷F₆, ⁵D₄→⁷F₅, and ⁵D₄→⁷F₄ transitions of Tb³⁺, respectively. Among them, the transition of ⁵D₄→⁷F₅ with green emission at 545 nm is predominant, which can be described by the large values of the reduced matrix elements at J = 5 and the Judd–Ofelt theory [24,25]. The relative intensity of Tb³⁺ (545 nm) emissions as functions of Tb³⁺ concentration for LMA: Tb³⁺ phosphors are shown in the inset of Fig. 3(b). It is found that the relative emission intensity of Tb³⁺ at 545 nm initially increases up to 2 mol% and then decreases when Tb³⁺ concentration further increases. Hence the optimal doping concentration has been found that about 2 mol%.

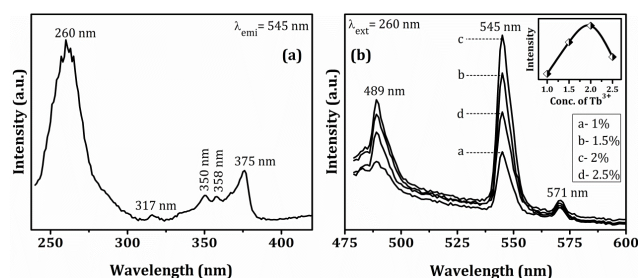


Fig. 3. (a) PL excitation (PLE) spectrum of LMA: 0.02Tb³⁺ phosphor. (b) PL spectra of LMA: Tb³⁺ phosphors. Inset shows dependence of emission intensity on content of Tb³⁺ in LMA: Tb³⁺ phosphors.

In Fig. 4(a), the PLE spectrum of LMA: Sm³⁺ (1.5 mol%) phosphor (monitored at 602 nm) shows several peaks, which are located at 343, 360, 375, 403,

417, 438, 462, and 470 nm. These excitation lines are corresponding to the electronic transitions of ⁶H_{5/2}→⁴K_{15/2}, ⁶H_{5/2}→⁴D_{3/2}, ⁶H_{5/2}→⁶P_{7/2}, ⁶H_{5/2}→⁴F_{7/2}, ⁶H_{5/2}→⁶P_{5/2}, ⁶H_{5/2}→⁴G_{9/2}, ⁶H_{5/2}→⁴I_{9/2}, and ⁶H_{5/2}→⁴I_{13/2}, respectively [26]. Among all these peaks, the strongest one belongs to the ⁶H_{5/2}→⁴F_{7/2} transition at 403 nm in the range of n-UV wavelength, which makes LMA: Sm³⁺ phosphors suitable for white lighting devices based on GaN LEDs. Figure 4(b) depicts the PL emission spectra of LMA: Sm³⁺ phosphors by monitoring emission wavelength at 403 nm. It consists of four characteristic emission peaks at 566, 603, 651, and 707 nm which are assigned to ⁴G_{5/2}→⁶H_{5/2}, ⁴G_{5/2}→⁶H_{7/2}, ⁴G_{5/2}→⁶H_{9/2}, and ⁴G_{5/2}→⁶H_{11/2} transitions of Sm³⁺, respectively. Among these emission peaks, the transition at 603 nm (⁴G_{5/2}→⁶H_{7/2}) had the maximum intensity than other three transitions, which corresponds to red emission of LMA: Sm³⁺ phosphors. The selection rule ΔJ = ±1, (where J = angular momentum) satisfied by strongest transition ⁴G_{5/2}→⁶H_{7/2} (603 nm) which reveals it is a partly magnetic dipole (MD) and partly electric dipole (ED) natured. Furthermore, the peak at 566 nm (⁴G_{5/2}→⁶H_{5/2}) is MD transition natured and another peak at 651 nm (⁴G_{5/2}→⁶H_{9/2}) is purely ED transition natured, which is very sensitive to the crystal field. Frequently, to recognize the symmetry of the surrounding environment of the trivalent 4f ions, intensity ratio ED/MD can be used, which can be related to the site symmetry around the Sm³⁺ ions in the host matrix. When the ED transition is more intense than the MD transition then asymmetric nature is dominated [27]. In the present work, the emission intensity of ⁴G_{5/2}→⁶H_{5/2} (MD) transition is higher than that of ⁴G_{5/2}→⁶H_{9/2} (ED) transition, indicating the symmetric nature of Sm³⁺ ions in LMA host matrix. Inset of Fig. 4(b) shows the dependence of emission intensity on the content of Sm³⁺ in LMA: Sm³⁺ phosphors. The maximum emission intensity is observed at 1.5 mol% concentration of Sm³⁺ ions.

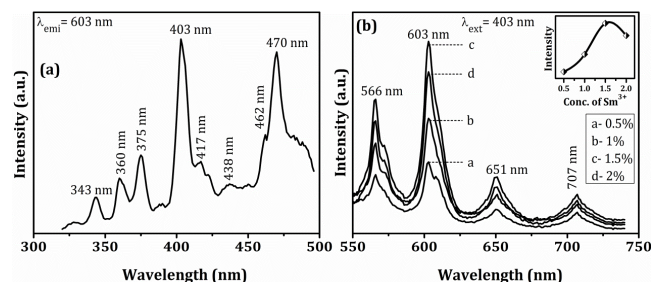


Fig. 4. (a) PLE spectrum of LMA: 0.015Sm³⁺. (b) PL emission spectra of LMA: Sm³⁺. Inset shows dependence of emission intensity on content of Sm³⁺ in LMA: Sm³⁺ phosphors.

Energy transfer mechanism in LMA: Tb³⁺, Sm³⁺

Figure 5(a) depicts the comparison of PLE spectra of Tb³⁺ and Sm³⁺ ions individually and co-doped LMA phosphors by monitoring the Tb³⁺ (545 nm) and Sm³⁺ (603 nm) emission wavelengths. The excitation spectra of Tb³⁺ and Tb³⁺/Sm³⁺ doped LMA phosphors by monitoring the Tb³⁺

emission wavelength at 545 nm shows similar excitation peaks with strong broadband due to $4f^8 \rightarrow 4f^75d$ transition of Tb^{3+} centered at 260 nm in the lower wavelength region and weak $f \rightarrow f$ transitions of Tb^{3+} ions in the wavelength range of 300–380 nm without any Sm^{3+} excitation peaks (in Tb^{3+}/Sm^{3+} ions co-doped sample), as can be seen in the **Fig. 5(a)** [(i) & (iii)]. The only Sm^{3+} doped LMA phosphor excited at 603 nm exhibits strong $f \rightarrow f$ transitions in the lower energy side as shown in **Fig. 5(a)** [(ii)]. Similarly, when the PLE spectra of LMA: Tb^{3+}/Sm^{3+} phosphor are monitored at 603 nm (Sm^{3+} emission wavelength), strong $f \rightarrow d$ transition bands of Tb^{3+} ions in the higher energy region and strong $f \rightarrow f$ transitions bands of Sm^{3+} ions in the lower energy region are seen as shown in **Fig. 5(a)**[(iv)] [28]. All the excitation spectra of LMA phosphor at different emission wavelengths showed the common excitation band at 375 nm attributable to $^7F_6 \rightarrow ^5G_6$ of Tb^{3+} ion and $^6H_{5/2} \rightarrow ^6P_{7/2}$ of Sm^{3+} ion [29].

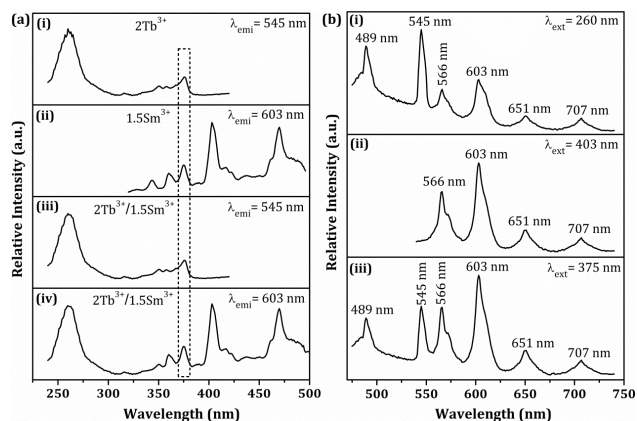


Fig. 5. (a) PLE spectra of $2Tb^{3+}$, $1.5Sm^{3+}$ and $2Tb^{3+}/1.5Sm^{3+}$ doped LMA phosphors by monitoring the emission wavelengths of 545 and 603 nm (the highlighted line shows the common excitation peak). (b) PL spectra of $2Tb^{3+}/1.5Sm^{3+}$ doped LMA phosphor at the excitation wavelengths of 260, 403 and 375 nm.

Fig. 5(b) depicts the PL spectra of LMA: $0.02Tb^{3+}/0.015Sm^{3+}$ phosphor obtained at excitation wavelengths of 260, 403, and 375 nm. The LMA: $0.02Tb^{3+}/0.015Sm^{3+}$ phosphor shows the green emission bands of Tb^{3+} ions including weak Sm^{3+} transitions obtained upon excitation at 260 nm wavelengths. Only Sm^{3+} emission bands without Tb^{3+} emission at 566, 603, 651, and 707 nm due to $^4G_{5/2} \rightarrow ^6H_{5/2}$, $^4G_{5/2} \rightarrow ^6H_{7/2}$, $^4G_{5/2} \rightarrow ^6H_{9/2}$, and $^4G_{5/2} \rightarrow ^6H_{11/2}$ transitions, respectively, are observed upon excitation at 403 nm wavelengths. It is caused by the overlapping of the Sm^{3+} ($^6G_{5/2} \rightarrow ^6H_{7/2}$) emission with the tail of Tb^{3+} ($^5D_4 \rightarrow ^7F_4$) emission. However, the common excitation wavelength of 375 nm can be found for LMA: Tb^{3+}/Sm^{3+} phosphors. At the common excitation of 375 nm, PL spectra shows three groups of emission bands blue region related to the electronic transitions $^5D_3 \rightarrow ^7F_J$ ($J = 5, 4, 3,$ and 2), green region $^5D_4 \rightarrow ^7F_J$ ($J = 6, 5,$ and 4) of Tb^{3+} , and orange-red region $^4G_{5/2} \rightarrow ^6H_{J/2}$ ($J = 5, 7, 9,$ and 11) transitions of Sm^{3+} ,

respectively due to the ET from Tb^{3+} to Sm^{3+} ions. As compared to the blue emission, the green emission was dominant in the emission spectrum, so we observed only the green emission with the naked eye.

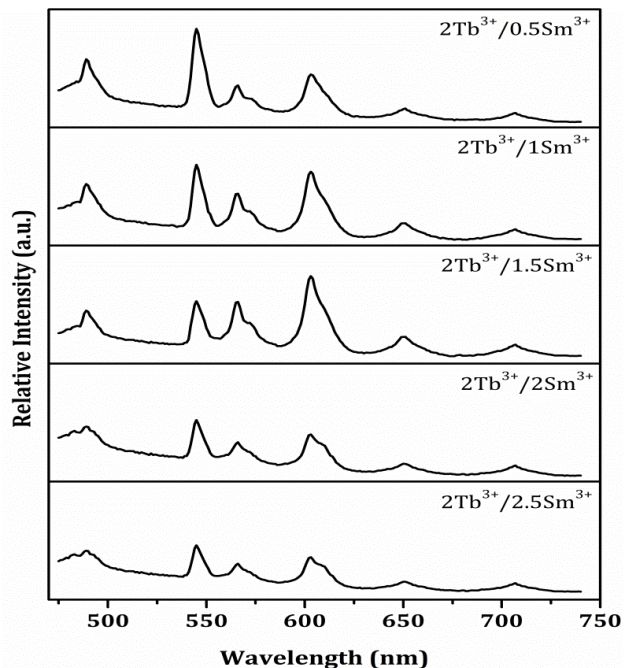


Fig. 6. PL spectra of LMA: $2Tb^{3+}/Sm^{3+}$ at different concentrations of Sm^{3+} ions under 375 nm common excitation.

Fig. 6 depicts the PL spectra of the LMA: $2Tb^{3+}/Sm^{3+}$ samples with different concentrations of Sm^{3+} under common excitation at 375 nm. It can be seen that with increasing Sm^{3+} concentration, the emission intensity of Tb^{3+} ions reduces while it is of Sm^{3+} ion enhances due to the efficient ET from Tb^{3+} to Sm^{3+} ions. It reveals that the Sm^{3+} ions sensitized by Tb^{3+} ions through ET and the energy is transferred from Tb^{3+} to Sm^{3+} . However, it is clear that, upon increasing the Sm^{3+} content above 1.5 mol%, the intensities of the Sm^{3+} emission begin to reduce as a result of a self-quenching effect (SQE) due to the interactions between Sm^{3+} ions [30]. **Fig. 7(a)** depicts the dependence of emission intensities of Tb^{3+} at 545 nm, Sm^{3+} at 603 nm and ET efficiency of $Tb^{3+} \rightarrow Sm^{3+}$ as a function of Sm^{3+} concentrations.

The ET efficiency (η_T) from sensitizer Tb^{3+} to activator Sm^{3+} in LMA: Tb^{3+}/Sm^{3+} samples can be approximately evaluate according to the data of intensity by using following formula.

$$\eta_T = 1 - [I_s/I_{s0}] \quad (1)$$

where I_s and I_{s0} are the luminescence intensity of sensitizer Tb^{3+} ions in the presence and absence of activator Sm^{3+} ions, respectively. The evaluate ET efficiency for different concentrations of Sm^{3+} ions were 30% (0.5 mol%), 52.1% (1 mol%), 62.19% (1.5 mol%), 69.23% (2 mol%), and 78.28% (2.5 mol%). It can be seen that the ET efficiency increases with increasing Sm^{3+}

concentration, and reaches 78.28% at 2.5 mol%, demonstrating that the ET from Tb³⁺ to Sm³⁺ is efficient. Moreover, the critical distance (R_c) in LMA: Tb³⁺/Sm³⁺ phosphor also can be estimated through the formula suggested by Blasse [31],

$$R_c \approx 2 \left[\frac{3V}{4\pi X_c N} \right]^{1/3} \quad (2)$$

where V is the volume of the unit cell, X_c is the critical concentration, and N represents the number of Z ions in the unit cell. For LMA host, $V = 686.21 \text{ \AA}^3$, $N = 2$ and X_c is the sum content of Tb³⁺ and Sm³⁺ ions, at which the luminescence intensity of Tb³⁺ ions is half of that in the absence of Sm³⁺ and found to be 0.03 mol from the Fig. 7(a). The critical distance (R_c) is estimated to be about 27.96 Å. Since the value of R_c is much longer than 5 Å, this implies that the exchange interaction would not be responsible for the ET mechanism from Tb³⁺ to Sm³⁺ ions. Consequently, only electric multipolar interactions contribute to the ET mechanism in this case. To understand the multipolar interactions, following relationship can be obtained [32],

$$\frac{I_{so}}{I_s} \propto C^{n/3} \quad (3)$$

where I_s and I_{so} are the luminescence intensity of sensitizer Tb³⁺ ions in the presence and absence of activator Sm³⁺ ions, respectively. C is the total concentration of Tb³⁺ and Sm³⁺ ions. The relationships between I_{so}/I_s and $C^{n/3}$ based on the Eq. (3) are illustrated in Fig. 7(b). The linear behavior was observed only when $n = 6$, indicating that the ET from Tb³⁺ to Sm³⁺ ions in LMA: Tb³⁺/Sm³⁺ phosphor takes place through the dipole-dipole interactions mechanism. All results suggest that Tb³⁺ ions act as a sensitizer when co-doped with Sm³⁺ ions and also such combination of dual RE ions doped optical materials find potential applications as multicolor emitting phosphor.

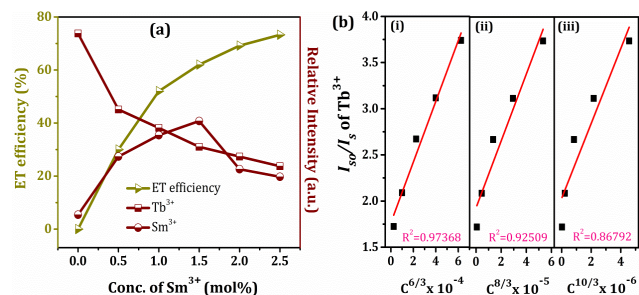


Fig. 7. (a) Dependence of the emission intensity of Tb³⁺, Sm³⁺ ions and ET efficiency on the Sm³⁺ concentration in LMA:Tb³⁺/Sm³⁺ phosphors. (b) Dependence of I_{so}/I_s of Tb³⁺ on (i) $C^{6/3}$, (ii) $C^{8/3}$, (iii) $C^{10/3}$, respectively.

Conclusions

A series of Tb³⁺/Sm³⁺ single as well as co-doped LMA phosphors with tetragonal structure were successfully synthesized by using low-temperature solution combustion technique. The critical distance (R_c) has been calculated by the concentration quenching method and it is found to

be 27.96 Å. The ET efficiency also has been calculated, it increases with increasing Sm³⁺ doping content, and its value was estimated to be 78.28% when the content of Sm³⁺ was up to 2.5 mol%. This shows efficient ET from Tb³⁺ to Sm³⁺ in LMA: Tb³⁺/Sm³⁺ phosphor. LMA: Tb³⁺/Sm³⁺ phosphor exhibited great potential applications as multicolor emitting phosphor for solid-state lighting.

Acknowledgement

Author SPP is thankful to management of the Institution KNM, Nagpur for providing useful facilities of the instrumentation, SHIMADZU Spectro fluorophotometer (RF-5301 PC).

Keywords

LaMgAl₁₁O₁₉, luminescence, energy transfer, dipole-dipole interaction, concentration quenching.

Received: 22 May 2020

Revised: 22 July 2020

Accepted: 01 September 2020

References

- Blasse G, Grabmaier BC. Luminescent Material. Springer-Verlag, Berlin Heidelberg New York London Paris Tokyo Hong Kong Barcelona Budapest: Springer-Verlag Berlin Heidelberg New York; **1994**. 1-232.
- Li, B.; Sun, Q.; Wang, S.; Guo, H.; Huang, X.; *RSC Adv.*, **2018**, *8*, 9879.
- Guan, H.; Liu, G.; Wang, J.; Dong, X.; Yu, W.; *Dalt Trans.*, **2014**, *43*, 10801.
- Zhou, J.; Xia, Z.; *J. Mater Chem. C.*, **2014**, *2*, 6978.
- Liu, T.; Meng, Q.; Sun, W.; *J. Lumin.*, **2016**, *170*, 219.
- Mendhe, M.S.; Puppalar, S.P.; Dhoble, S.J.; *Luminescence: Journal of Bio and Chem Luminescence*, **2016**, *31*, 881.
- Premkumar, H.B.; Sunitha, D.V.; Singh, F.; Nagabhushana, H.; Sharma, S.C.; Nagabhushana, B.M.; et al. *J. Lumin.*, **2012**, *132*, 2679.
- Yang, C.; Liu, Q.; Huang, D.; Li, X.; Zhang, X.; Bai, Z.; Wang, X.; Mia, X.; *J. Lumin.*, **2019**, *214*, 116541.
- Li, Z.; Zhong, B.; Cao, Y.; Zhang, S.; Lu, Y.; Mu, Z.; Hu, Z.; Hu, Y.; *J. Mater. Science: Mater. Electronics.*, **2019**, *30*, 10491.
- Yang, C.; Li, X.; Liu, Q.; Xang, X.; Bai, X.; Wang, X.; Mi, X.; *J. Mater. Science: Mater. Electronics*, **2020**, *31*, 1057.
- Suchithra, V.G.; Rao, P.P.; Aswathy, B.A.; *J. Mater. Science: Mater. Electronics*, **2020**, *31*, 5141.
- Kumar, K.A.; Babu, S.; Prasad, V.R.; Damodaraiah, S.; Ratnakaram, Y.C.; *Mater. Res. Bull.*, **2017**, *90*, 31.
- Li, K.; Shang, M.; Lian, H.; Lin, J.; *J. Mater. Chem. C.*, **2016**, *4*, 5507.
- Mendhe, M.S.; Puppalar, S.P.; Dhoble, S.J.; *Optik*, **2018**, *166*, 15.
- Mendhe, M.S.; Puppalar, S.P.; Dhoble, S.J.; *Optical Materials*, **2018**, *82*, 47.
- Sheng, T.; Fu, Z.; Wang, X.; Zhou, S.; Zhang, S.; Dai, Z.; *J. Phys. Chem. C.*, **2012**, *116*, 19597.
- Reddy, C.P.; Naresh, V.; Ramaraghavulu, R.; Rudramadevi, B.H.; Reddy, K.T.R.; Buddhudu, S.; *Spectrochim ACTA PART A Mol Biomol Spectrosc.*, **2015**, *144*, 68.
- Liu, H.; Liao, L.; Chen, J.; Guo, Q.; Zhang, Y.; Mei, L.; *J. Lumin., Elsevier*, **2016**, *169*, 739.
- Min, X.; Fang, M.; Huang, Z.; Liu, Y.; Tang, C.; Zhu, H.; et al. *Opt Mater.*, **2014**, *37*, 110.
- Min, X.; Huang, Z.; Fang, M.; Liu, Y.; Tang, C.; Wu, X.; *Inorg Chem.*, **2014**, *53*, 6060.
- Ballesteros, C.; Gonza ´lez R.; Chen, Y.; Kokta, M.R.; *Phys. Rev. B: Condens. Matter.*, **1993**, *47*, 2460.
- Sun, J.; Sun, Y.; Lai, J.; Xia, Z.; Du, H.; *J. Lumin.*, **2012**, *132*, 3048.
- Naresh, V.; Buddhudu, S.; *J. Lumin.*, **2013**, *137*, 15.
- Wen, Y.; Wang, Y.H.; Zhang, F.; Liu, B.T.; *Mater Chem Phys. B.V.*; **2011**, *129*, 1171.

25. Rao, V.; Kumar, B.; Jayasimhadri, M.; Jang, K.; Lee, H.; Yi, S.; et al. *J. Cryst Growth*, **2011**, 326, 120.
26. Gupta, S.K.; Pathak, N.; Thulasidas, S.K.; Natarajan, V.; *J. Lumin.*, **2016**, 169, 669.
27. Gupta, S.K.; Ghosh, P.S.; Pathak, N.; Arya, A.; Natarajana, V.; *RSC Adv.*, **2014**, 4, 29202.
28. Pavitra, E.; Raju, GSR.; Ko, Y.H.; Yu, J.S.; *Phys. Chem. Chem Phys.*, **2012**, 14, 11296.
29. Jeon, Y.; Bharat, L.K.; Yu, J.S.; *J. Lumin.*, **2015**, 166, 93.
30. Lakshminarayana, G.; Yang, R.; Qiu, J.R.; Brik, M.G.; Kumar, G.A.; Kityk, I.V.; *J. Phys. D Appl Phys.*, **2009**, 42, 015414.
31. Blasse, G.; *Philips Res Rep.*, **1969**, 24, 131.
32. Dexter, D.L.; Schulman, J.H.; *J. Chem Phys.*, **1954**, 22, 1063.

Authors biography



Dr. Suresh Puppalwar obtained M.Sc. and Ph.D. degree in Physics from RTM Nagpur University, Nagpur, India. He is presently working as Associate Professor in Department of Physics, Kamlā Nehru Mahavidyalaya, Nagpur, India. His research of interest is synthesis and characterization of luminescent materials for solid state lighting and development of TLD phosphors for radiation dosimetry. He is an active member of Luminescence Society of India. He is also a member of IAAM.



Dr. Mukesh Mendhe has done his M.Sc. and Ph.D. degree from Department of Physics, Kamlā Nehru Mahavidyalaya, Nagpur, affiliated to RTM Nagpur University, Nagpur. His research work is on energy transfer in luminescent materials applied for solid state lighting.



Dr. S.J. Dhoble is currently working as a Professor in the Department of Physics, R.T.M. Nagpur University, Nagpur-India. Prof. Dhoble published more than 500 research papers in peer reviewed journals on solid-state lighting, LEDs, radiation dosimetry and laser materials and has one international patent. He is author of 23 books/Chapters. He received Outstanding Scientist-2015 award in outstanding research contribution in Solid State Physics at Chennai from Venus International Foundation. He is the Editor of Luminescence: The Journal of Biological and Chemical Luminescence, John Wiley & Sons Ltd.